PEARLTHANE® 11T85UV

Thermoplastic Polyurethane Elastomer

PEARLTHANE® 11T85UV is a UV-resistant polycaprolactone copolyester based TPU, supplied in form of translucent, colourless pellets, featuring adequate hardness with excellent flow and mechanical properties. It can be injection-moulded and coextruded.

TYPICAL PROPERTIES

Property	Test Method	Typical Values *
Density @ 20ºC	DIN 53.479	1.16 g/cm^3
Shore Hardness	DIN 53.505	86 A
Tensile Strength	DIN 53.504	40 MPa
Elongation @ Break	DIN 53.504	630 %
Modulus @ 100% Elongation	DIN 53.504	6 MPa
Modulus @ 300% Elongation	DIN 53.504	10 MPa
Tear Strength	DIN 53.515	90 kN/m
Abrasion Loss	DIN 53.516	25 mm^3
Compression Set *(70 h. @ 23ºC)*	ASTM D395B	20 %
Compression Set *(24 h. @ 70ºC)*	ASTM D395B	35 %
Moisture Content	MQSA 44	< 0.1 %
Melting Range *(MFI=10**)*	MQSA 111	178 – 188 ºC
Tg. *(DSC, 10ºC / min.)*	DIN 51.007	- 40 ºC

** These are typical values & should not be used for establishing specifications.*
*** Temperature at which MFI = 10 g/10 min @ 21.6 kg.*

WORKING INSTRUCTIONS

For optimum results, previous drying of the product during 1-2 hours at 100-110º C is advisable, in a hot air circulatory, vacuum or desiccant-air dryer.

EXTRUSION

In accordance with our experience, the characteristics of the extruder that is suitable for processing **PEARLTHANE® 11T85UV** are the following:

1. L/D ratio between 25:1 and 30:1
2. The extruder screw must have 3 zones and a compression ratio in between 2:1 and 3:1 (Usually, the screws that are used for Polyethylene extrusion give good results).
3. The extruder screw should have a continuous regulation device and a working power higher than for processing other plastics.
4. The speed of the extruder should be low (12 to 60 rpm, depending on its diameter), so as to avoid material degradation due to shearing.

Merquinsa's Products are sold subject to Merquinsa's General Sales Conditions printed on the back of invoices and other shipping documents (available upon request). This is correct information based on our experience, and is given in good faith and without compromise. Each purchaser bears full responsibility for the application, use and processing of Merquinsa's products described herein, as well as their suitability to the purchaser's specific application, as this is beyond Merquinsa's control.

Gran Vial, 17 08160 Montmeló, Spain Tel. (34) 93 572 11 00 Fax (34) 93 572 09 34
E-mail: info@merquinsa.com http://www.merquinsa.com
Registered in Barcelona Trade Register under Tax Identification Number B08530305, volume 31186, folio 106, page B-30777, entry 12.

ISO 9001 CERTIFICATED FIRM
ISO 14001 CERTIFICATED FIRM
Responsible Care®

5. The filters used should be disks with holes of 1.5 to 5 mm. (depending on the screw and the die), and screen packs (the no. of meshes /cm^2 will depend on the end product that is processed), so as to create a pressure built-up.

The suggested processing-temperature profiles for film extrusion (flat films) are depicted in the figure below:

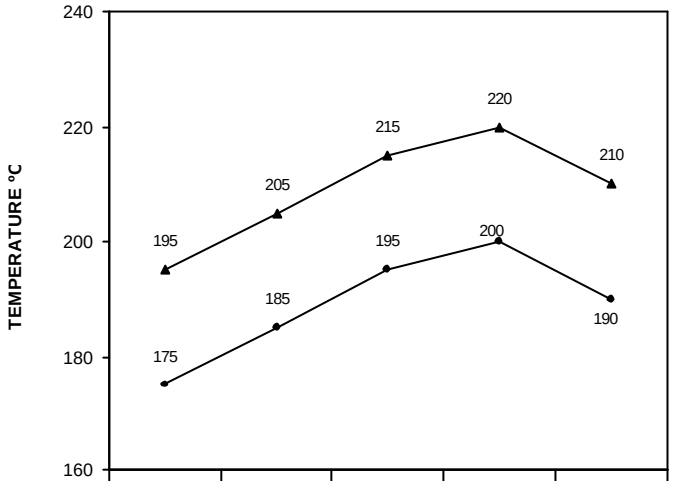

	1	2	3	4	DIE
PROFILE 11T85UV/1	175	185	195	200	190
PROFILE 11T85UV/2	195	205	215	220	210

EXTRUDER & CONDITIONS

TYPE.- 30/25D (L/D=25:1), COOLING.- Air, SCREW.- 3:1, SPEED.- 20-50 rpm., BREAKER PLATE.- --. FILTER PACK.- --. THICKNESS DIE.- 0.2 mm. PRE-DRYING.- 1 h @ 105 ºC

INJECTION MOULDING

Based on an injection moulding equipment with the following characteristics:

Closing force:	: 30 tons
Screw diameter:	: 26 mm
L/D ratio:	: 23
Maximum hydraulic pressure:	: 210 bar
Mould:	: Plaque 120x120x2 mm

Merquinsa's Products are sold subject to Merquinsa's General Sales Conditions printed on the back of invoices and other shipping documents (available upon request). This is correct information based on our experience, and is given in good faith and without compromise. Each purchaser bears full responsibility for the application, use and processing of Merquinsa's products described herein, as well as their suitability to the purchaser's specific application, as this is beyond Merquinsa's control.

Gran Vial, 17 08160 Montmeló, Spain Tel. (34) 93 572 11 00 Fax (34) 93 572 09 34
E-mail: info@merquinsa.com http://www.merquinsa.com
Registered in Barcelona Trade Register under Tax Identification Number B08530305, volume 31186, folio 106, page B-30777, entry 12.

ISO 9001 CERTIFICATED FIRM
ISO 14001 CERTIFICATED FIRM
Responsible Care®

The suggested processing conditions are the following:

INJECTION CONDITIONS

Feed zone	195ºC	Injection pressure	100 bar
Compression zone	200ºC	Injection time	2.8 sec
Metering zone	210ºC	Holding pressure	60 bar
Nozzle	210ºC	Holding time	15 sec
Mould temperature	35ºC	Cooling time	10 sec

Screw speed : approx. 105 rpm.

APPLICATIONS

PEARLTHANE® 11T85UV when processed by injection moulding, can be used for making automotive and a variety of technical components.

PEARLTHANE® 11T85UV when processed by coextrusion, can be used for making technical sheets thanks to its excellent adhesion into polar substrates such as ABS, PC and PVC.

HEALTH AND SAFETY

A safety data sheet on **PEARLTHANE® 11T85UV** is available, with all the information related to safety.

PACKAGING

PEARLTHANE® 11T85UV is packaged in heat-sealed, moisture proof multi–layer bags of 25 Kg net weight made of PE/Aluminium/PE. Bags are shipped on pallets of 750 Kg. Additionally, PE-lined cardboard gaylords of 700 Kg net weight are available.

STORAGE

Material received from Merquinsa should be inspected to assure the containers are not damaged during transportation before being stored prior to use. **PEARLTHANE® 11T85UV** should be kept in a cool (15-25ºC) and dry environment prior to being processed. Standard practice of consuming resin on first-in first-out basis should be employed.

For more information, please feel free to contact us at **www.merquinsa.com**

Merquinsa's Products are sold subject to Merquinsa's General Sales Conditions printed on the back of invoices and other shipping documents (available upon request). This is correct information based on our experience, and is given in good faith and without compromise. Each purchaser bears full responsibility for the application, use and processing of Merquinsa's products described herein, as well as their suitability to the purchaser's specific application, as this is beyond Merquinsa's control.

Gran Vial, 17 08160 Montmeló, Spain Tel. (34) 93 572 11 00 Fax (34) 93 572 09 34
E-mail: info@merquinsa.com http://www.merquinsa.com
Registered in Barcelona Trade Register under Tax Identification Number B08530305, volume 31186, folio 106, page B-30777, entry 12.

ISO 9001 CERTIFICATED FIRM
ISO 14001 CERTIFICATED FIRM
Responsible Care®